

Geometrical Arrangement in the Needle Loop of Multifilament Yarn using Genetic Algorithm

Ramin Bakhshpour, Saeed Ajeli, Hossein Hasani, Ali Asghar Asgharyan Jeddi

Department of Textile Engineering, Isfahan University of Technology, Isfahan IRAN

Correspondence to:
Saeed Ajeli email: sajeli@cc.iut.ac.ir

ABSTRACT

In this paper, the loop structure of plain knitted fabrics, constructed from multifilament yarns is geometrically modeled. This model is based on post-buckling behavior of multifilament yarns composed of two, three or seven filaments by assuming that their cross-section is circular. In the first step of modeling, 2-D post buckled shape of each filament within the yarn structure was investigated regarding the classic theory of *Elastica*. In this step, volumetric intersections between the filaments occurred. In the second step, the arrangement of the filaments in 3-D space after applying an out-plane bending force, was predicted. Genetic Algorithm was used to find the minimum bending force and reduced the volumetric intersections between the yarn's constitutive filaments using the Genetic Algorithm method, constant forces between the filaments is replaced with a concentrated out-plane force which results in reducing the problems of complexity and optimization. The geometry position of yarn filaments is also modeled using finite element method. Comparison of results indicated a small difference between the two models and confirms that the analytical proposed model is acceptable.

Keywords: needle loop; multifilament yarn; post-buckling; genetic algorithm; finite element method

INTRODUCTION

Understanding the loop geometry of knitted structures is very important in the study of dimensional and mechanical behavior of knitted fabrics. Leaf [1] proposed the mathematical model of *Elastica* used for loop structure. Munden [2] recommended a loop configuration obtained according to the minimum energy method conditions and suggested that his model is independent of yarn properties and stitch length. Grosberg [3] also worked on the geometrical properties of simple warp-knitted fabrics. An energy minimization technique has been also used to describe the shape of the single bar warp knitted fabric structures [4]. Recently, many researchers have worked on the loop geometry of the

fabrics. A new 3-D image of the basic warp-knitted structure was created in a CAD program by employing the data obtained from the loops of the fabric in real condition [5]. A mechanical model for knitted fabrics was developed using the energy model of knitted loop, in which the mechanical behavior of the curved yarn during the knitting was considered to be nonlinear. In the developed model, the effect of residual torque on the yarn was also taken into consideration [6, 7]. The 3-D model of a plain weft-knitted structure was resulted from the assumption that yarn cross section changes to ellipse during the loop formation [8]. In the other work, the geometrical model of a tuck stitch and its effect on the plain knitted fabric structure were introduced [9]. Also, the elliptical shape for the head of loops and general helices for the other parts such as the loop's arms were used for investigating the single pique, half and full cardigan weft knitted structures [10]. Using a buckled-twisted elastic rod, Ajeli et al. found a 3-D geometry of knitted loop structure [11]. Furthermore, Durville approached the textile simulation of woven structures problem at the fibers scale using 3-D beam model [12]. He also proposed a finite element approach for simulating the mechanical behavior of beam assemblies that are subjected to large deformations and also developing the contact-friction interactions [13]. Robitaille et al. presented an algorithm that generates geometric descriptions of unit cells of textiles and composite materials [14]. Lomove et al. used the finite element model of a unit cell of a textile in their investigations [15].

In the previous studies, modeling was mostly carried out on a plain knitted structure produced from monofilament yarns or the yarn structure has been assumed as a continuous media. In a real state, knitted loops are produced from multi-filaments yarns. Regarding *Elastica* theory, this study aimed at modeling loop geometry of a multifilament knitted structure.

3-D GEOMETRICAL LOOP MODEL

First Step, 2-D Post-Buckling

In order to simplify the proposed model, it is assumed that the multifilament yarns are composed of two, three and seven filaments circular cross section. Post-buckling behavior of multifilament yarns was investigated with respect toastica model (Figure 1). According to Leaf's Elastica formulation which describes the deflection of elastic rod, the dimension of the loop at any arbitrary point(x,y) is as follows [1]:

$$x=b[2E(\kappa,\varphi)-F(\kappa,\varphi)] \quad (1)$$

$$y=\pm 2b\kappa(\cos(\varphi)-\cos(\varphi_0)) \quad (2)$$

$$a=[2E(\kappa,\varphi_0)-F(\kappa,\varphi_0)]/F(\kappa,\varphi_0) \quad (3)$$

Where $F(\kappa,\varphi)$ is an elliptic integral of the first kind with modulus κ , $E(\kappa,\varphi)$ is an elliptic integral of the second kind in which modulus κ and index a are the proportion of distance of the base(AA') to the rod length. Parameter b can be obtained using the equation $b=\sqrt{B/P}$ and B and P denote the flexural rigidity and buckling load, respectively.

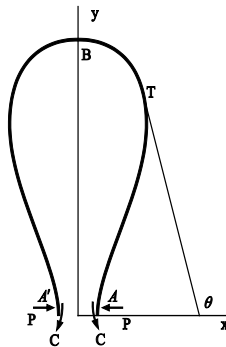


FIGURE 1. Elastica shape.

Solution procedure of Eq. (1), Eq. (2) and Eq. (3) with different base distance of Elastica curvature, by assuming the yarn cross section arrangement as shown in Figure 2 with circular cross section of diameter 1 cm and length of 100 cm of each monofilament is provided in Table I.

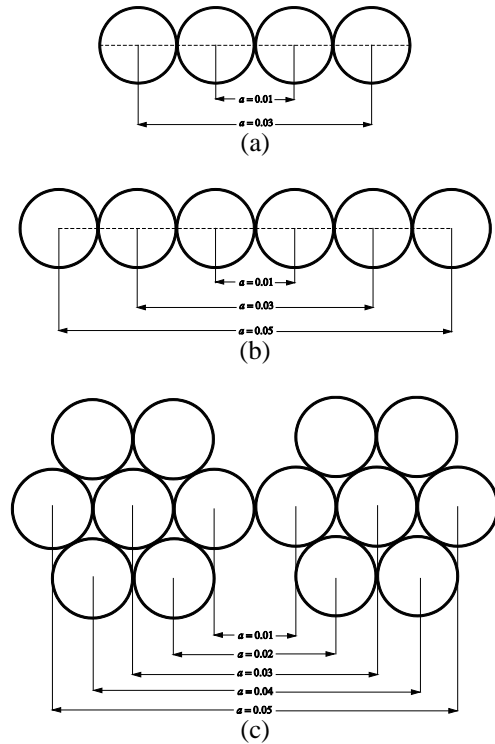


FIGURE 2. Proposed Elastica legs cross-section with different filaments arrangement. (a), (b) and (c) are ordered two, three and seven filaments yarn cross-section.

TABLE I. Critical results in 2-D Post-Buckling using Elastica model.

a	y_m	x_m
0.01	42.48	10.35
0.03	42.56	10.65
0.02	42.53	10.50
0.04	42.60	10.80
0.05	42.62	10.95

y_m and x_m are the maximum x and y.

Figures 3, 4 and 5 show the monofilament's position in the yarn using the proposed loop model for two, three and seven monofilament, respectively. Volumetric intersections between filaments can be easily seen in these figures which must be eliminated. Elimination process was performed using out-plane deflection method of mono filaments and Genetic Algorithm.

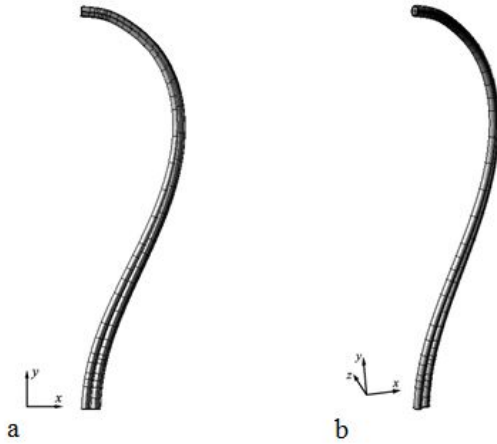


FIGURE 3. The shape of Post-Buckled yarn composed of 2 filaments, a. Front view b. Perspective view.

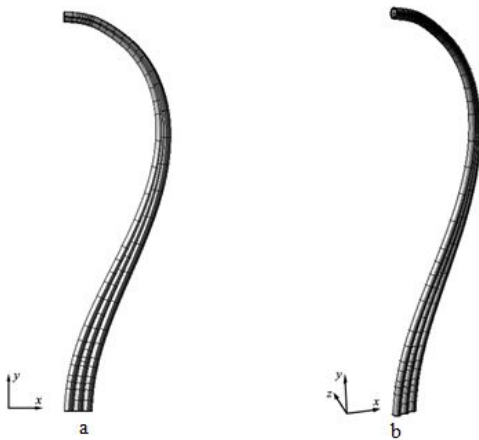


FIGURE 4. The shape of Post-Buckled yarn composed of 3 filaments, Front view b. Perspective view.

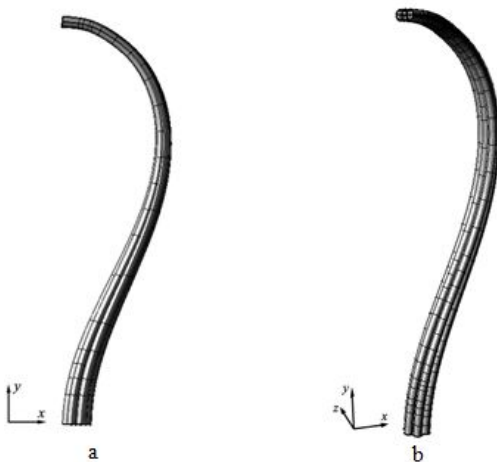


FIGURE 5. The shape of Post-Buckled yarn composed of 7 filaments, a. Front view b. Perspective view.

Second Step, Out-Plane Deflection

In this step, an out-plane bending force was used to eliminate the volumetric intersections of monofilament in the yarn model. Furthermore, Genetic Algorithm was utilized to reduce the problem complexity as well as optimize the contact force.

All the interactions on a filament have been replaced with an out-plane force on the loop head which causes bending in the YZ plane. The diagram of a simply supported beam under a concentrated load is illustrated In *Figure 6*. According to Bishop and Drucker [16], large deflection of a beam due to bending under a concentrated load can be expressed as follows:

$$Bd\phi/ds=P(L-\Delta-y) \quad (4)$$

Where B is bending rigidity, P is bending load, s and ϕ are arc length and slope angle, respectively. y is also the horizontal coordinate measured from the fixed end of the beam. L is the beam length. According to *Figure 6*, δ and Δ are structure deflection for corresponding θ and s .

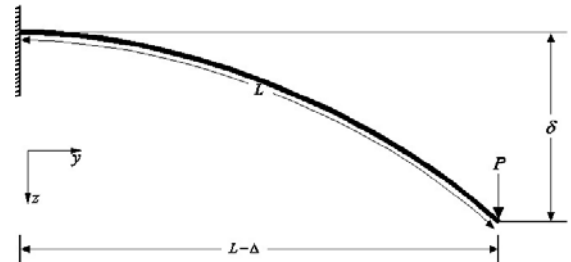


FIGURE 6. Large deflection of a beam using load F [16].

Solving Eq. (4), gives:

$$z = L \left(1 - \frac{2}{\alpha} [E(k, \theta) - E(k, \theta_1)] \right) \quad (5)$$

$$y = \sqrt{\frac{2P}{B}} (2k^2 - 2k^2 \sin^2 \theta)^{1/2} \quad (6)$$

Where $F(\kappa, \theta)$ and $E(\kappa, \theta)$ are elliptic integral of first and second kind with modulus κ , respectively and;

$$\alpha = F(k, \theta) - F(k, \theta_1) \quad (7)$$

$$1 + \sin \phi = 2k^2 \sin^2 \theta \quad (8)$$

If $\varphi = \varphi_0$ then $\theta = \theta_1$ and φ_0 denotes the tangent of free beam end.

Considering the last four equations, the 3-D shape of elastic in *Figures 3, 4 and 5* was achieved. Filament interactions complexity of this case would be resulted from friction, torsion, and bending forces that make the problem really complicated to be analytically solved. Numerical approaches are recommended in these situations; provided that filament interactions are simplified.

Genetic Algorithm (GA) was taken for optimizing the out-plane bending forces in the structure and elimination of volumetric intersection of the yarn filaments. GA is a search method in which the possible solutions space (search space) is studied to find an optimal solution. Each possible solution can be marked by its fitness value, depending on the problem definition. GA has a number of important features. The first feature is that it is a stochastic algorithm; randomness plays an essential role in GA. Second point is that a population of solution is taken into account. Keeping in memory more than a single solution offers a lot of advantages. The algorithm can recombine different solutions to get better ones and so, it can benefit from assortment. All the above mentioned features make GA a powerful optimization tool [17].

Each solution is represented through a chromosome. After encoding a solution into a chromosome, GA starts by generating an initial population of chromosomes. Generally the initial population is generated randomly. Then the GA loops over an iteration process to make the population evolve. Each iteration consists of the following steps: *Selection, Reproduction, Evaluation, and Replacement*.

In the present research, The GA's chromosome includes seven genes, one for each filament, holding the value of bending force. GA minimizes fitness function which is as follows [17]:

$$f(V) = \sum_{i=1}^6 \sum_{j=i+1}^7 V_{ij} \quad (9)$$

Where V_{ij} is volumetric intersection between i^{th} and j^{th} filament. Since $V_{ij} = V_{ji}$, the summations indexes which are chosen in a way to remove repetitive terms. By expansion the Eq. (9), it can be seen that there is no repetitive term in the fitness function. The above mentioned terms reduce the algorithm

performance and make the fitness function noisier. The Roulette Wheel was chosen as selection operator. Arithmetic crossover and uniform mutation were used for reproduction operator in which mutation and crossover rate were 0.8 and 0.01 respectively. Population number was 100. Arithmetic crossover operator linearly combines two parents using a weighting factor α according to the following expressions.

$$offspring1 = \alpha \text{ parent1} + (1 - \alpha) \text{ parent2}$$

$$offspring2 = (1 - \alpha) \text{ parent1} + \alpha \text{ parent2}$$

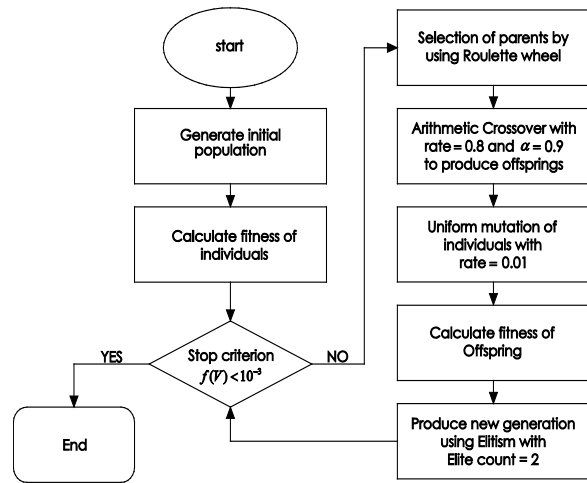


FIGURE 7. Flowchart of GA process.

The flowchart of GA process is shown in *Figure 7*. Optimization has been performed on three cases including 2, 3 and 7 filaments.

Case I

In this case, a yarn composed of two filaments has been optimized. Since the genes were known as the real values and the search space was very large, constrains have been defined to reduce the search space size and consequently computing time. Filaments bending directions are opposite; therefore one of them can bend in positive direction of axis z while another one bends in the reverse direction. It is clear that such constrain prevents the filaments from being on the same side of z -plane simultaneously.

Case II

The purpose of this case was to optimize a yarn composed of three filaments. Like the previous case, some constrains have been applied on filaments. In this case, bending directions of neighbor filaments are opposite. Filaments bending directions are depicted in *Figure 8*.

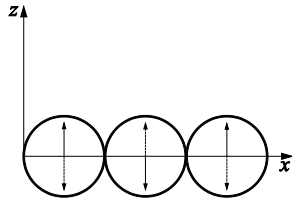


FIGURE 8. Bending direction of filaments in a yarn composed of 3 filaments.

Case III

In Case III a yarn composed of seven filaments has been optimized. In this case, optimization has been performed in two steps. In the first step, three filaments placed on plane $z=0$ have been optimized then in the second step, optimization of other four filaments has been carried out based on fix position of three initial ones. Constrains applied on filaments are shown in Figure 8. Bending directions of the filaments placed on plane $z=0$ are mutually opposite. Dashed directions in Figure 9 indicate this constrain.

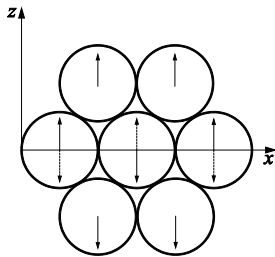


FIGURE 9. Bending direction of filaments in a yarn composed of 7 filaments.

GEOMETRIC LOOP MODEL RESULTS

The optimized structures of the 3-D yarn shape obtained by proposed model are illustrated in Figures 10, 11 and 12.

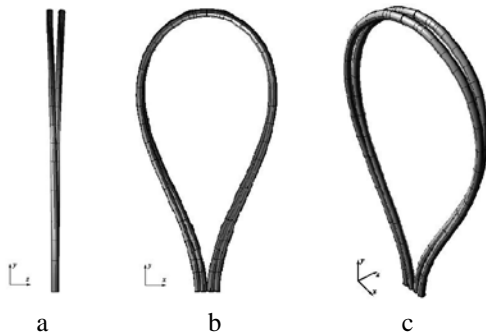


FIGURE 10. Optimal form of the yarn composed of 2 filaments obtained by proposed model. a, b and c is the side view, front view and 3-D view, respectively.

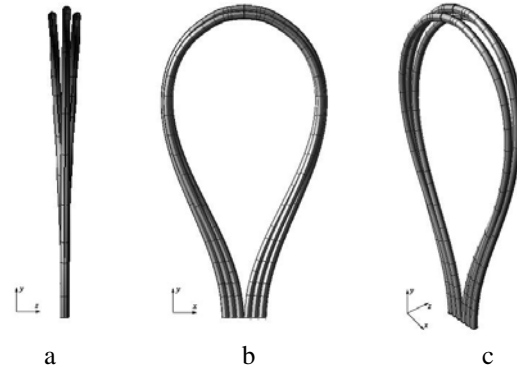


FIGURE 11. Optimal form of the yarn composed of 3 filaments obtained by proposed model. a, b and c is the side view, front view and 3-D view, respectively.

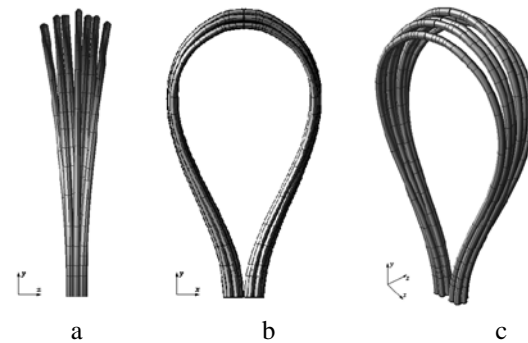


FIGURE 12. Optimal form of the yarn composed of 7 filaments obtained by proposed model. a, b and c is the side view, front view and 3-D view, respectively.

FINITE ELEMENT METHOD MODELING

The Finite element method (FEM) was utilized to verify the results of optimized yarn structure based on the proposed model. The Finite element method is a numerical computing technique for finding a solution for partial differential equations. The principle is to break a complicated problem into smaller interconnected sub-regions to facilitate solution procedure [18].

Yarn parameters modeled by finite element method are the same as those obtained from the proposed model. The yarn is composed of elastic rods with circular cross section of diameter 1 cm and length of 100 cm. Two, three and seven rods with arrangement illustrated in Figure 2 was considered for multifilament yarns FEM model. The main rod parameters of the structure used in FEM model are listed in Table II. The dynamic explicit method is considered for this analysis. For simple 2-D problems, static implicit analysis models are generally known to be more accurate and efficient than dynamic explicit analysis models. However, for complex 3-D forming problems, the static implicit

procedures encounter a number of inherent difficulties. Static implicit finite element formulations require a very long computational time for analyzing the model. The dynamic explicit method on the other hand, appears to be very effective in analyzing complex incremental forming problems. In this paper, a comparison of the analysis results has been obtained using dynamic explicit finite element method. *Figure 13* depicts illustrations of filament position in the loop structure.

TABLE II. Setting for finite element modeling of the problem.

Parameters	Value
Solver	Dynamic/ Explicit
Friction Coefficient	0.8
Element Type	3D Stress
Elements No.	400 per filament
Shape/Type	Solid/Sweep
Young's Modulus	200 GPa
Poisson's Ratio	0.3
Mass Density	7870 Kg/m ³
Section	Solid, Homogeneous

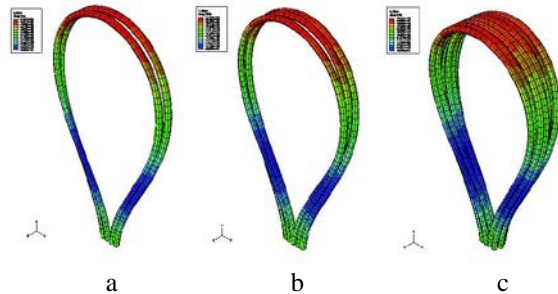


FIGURE 13. Finite element results. a, b, and c is a loop composed of 2, 3 and 7 rods, respectively.

COMPARING LOOP MODEL AND FEM

The results of the proposed loop model and FEM model have been compared. The results of the proposed model are listed in *Tables III, IV and V*, respectively. The indexes d , D and z_{max} are maximum width, maximum height and maximum deflection of the filament along z direction, respectively. Bending load F corresponds with calculated force of respective filament in the yarn. Plus and minus sign of the F shows the direction of the force along z direction which is known as the bending direction of the filament. $-z$ and $+z$ in *Tables III, IV, and V* show the initial position of the filament in negative and positive space of z plane, respectively.

Comparison between two models is provided in *Table VI*. The percentage of error is calculated as below:

$$\%Error = \frac{V_p - V_{fem}}{V_{fem}} \times 100 \quad (10)$$

Where V_p and V_{fem} account for values of the proposed and finite element model, respectively. Maximum error happens in z direction of the yarn which is composed of two filaments. Small amount of error in all cases shows that the proposed model's results are acceptable.

TABLE III. Proposed model results for the yarn composed of 2 filaments.

a	Bending Load F	d (cm)	D (cm)	Z_{max} (cm)
0.01	0.035	20.69	41.92	-0.95
0.03	0.032	21.25	42.05	+0.87

TABLE IV. Proposed model results for the yarn composed of 3 filaments.

a	Bending Load F	d (cm)	D (cm)	Z_{max} (cm)
0.01	-0.056	20.70	41.57	-1.52
0.03	+0.055	21.25	41.67	+1.50
0.05	-0.010	21.88	42.46	-0.27

TABLE V. Proposed model results for the yarn composed of 7 filaments.

a	Bending Load F	d (cm)	D (cm)	Z_{max} (cm)
0.01	0.056	20.69	41.57	-1.52
0.03	0.055	21.25	41.67	+1.50
0.05	0.010	21.88	42.46	-0.27
$-z$ 0.02	0.065	20.97	41.46	-2.63
$+z$ 0.02	0.013	20.96	40.33	+4.41
$-z$ 0.04	0.119	21.56	40.60	-4.11
$+z$ 0.04	0.065	21.56	41.53	+2.64

TABLE VI. Comparison between proposed model and finite element models.

	n	d (cm)	Error %	D (cm)	Error %	$Z_{z_{max}}$ (cm)	Error %
Proposed Model	2	21.25	2.1	42.05	3.2	1.82	4.0
FEM Model		21.70		43.43		1.89	
Proposed Model	3	21.88	3.4	42.46	2.1	3.02	2.8
FEM Model		22.65		43.36		2.93	
Proposed Model	7	21.88	2.1	42.46	3.0	8.52	2.5
FEM Model		22.35		43.78		8.74	

CONCLUSION

In the present study a geometrical model of a multifilament yarn is proposed. The model is composed of two steps including 2-D post-buckling of the filaments yarn and 3-D optimization of the filament interactions using genetic algorithm. In the first step, the multifilament yarn undergoes 2-D post-buckling phenomenon. It is shown that there are volumetric overlaps between post-buckled filaments which are needed to be eliminated. Determining the deflection of the knitted structure is analytically impossible, since there is a complicated collection of interactions between filaments during the post-buckling process. The interactions are replaced by an out-plane force through the Genetic Algorithm analysis which causes the filaments to be bent along the out-plane direction. Step two is associated with determining the force using genetic algorithm. Fitness function of the genetic algorithm is a summation of the overlaps between 2-D post-buckled filaments and is needed to be minimized. In order to verify the results of the proposed model, the yarn is modeled by the finite element method. The small difference between the two models confirms the acceptability of the proposed model.

REFERENCES

- [1] Leaf, G.A.V., "A Property of a Buckled Elastic Rod", *British Journal of Applied Physics*, Vol.9, 71-72, 1958.
- [2] Munden, D. L., "The Geometry and Dimensional Properties of Plain Knit Fabrics", *Journal of the Textile Institute*, Vol.50, 448-471, 1959.
- [3] Grosberg, P., "The Geometrical Properties of Simple Warp-knit Fabrics", *Journal of the Textile Institute*, Vol.55, No.1, 18-30, 1964.
- [4] Hart, K., De Jong, S. and R. Postle, "Analysis of the Single Bar Warp Knitted Structure Using an Energy Minimization Technique, Part I: Theoretical Development", *Textile Research Journal*, Vol.55, No.8, 489-498, 1985.
- [5] Goktepe, O. and Harlock, S.C., "A 3D Loop Model for Visual Simulation of Warp-knitted Structure", *Journal of the Textile Institute*, Vol.93, 11-28, 2002.
- [6] Choi, K.F. and Lo, T.Y., "An Energy Model of Plain Knitted Fabric", *Textile Research Journal*, Vol.73, No.8, 739-748, 2003.
- [7] Choi, K.F. and Lo, T.Y., "The Shape and Dimensions of Plain Knitted Fabric: A Fabric Mechanical Model", *Textile Research Journal*, Vol.76, No.10, 777-786, 2006.
- [8] Kyosev, Y., Angelova, Y., and Kovar, R., "3D Modeling of Plain Weft Knitted Structures of Compressible Yarn", *Research Journal of Textile and Apparel*, Vol.9, No.1, 88-97, 2005.
- [9] Tuba Alpyidiz and Arif Kurbak, "A Geometrical Model for the Single Pique (Lacoste) Knits", *Textile Research Journal*, Vol.76, No.11, 861-867, 2006.
- [10] Arif Kurbak and Ozlem Kayacan, "Basic Studies for Modeling Complex Weft Knitted Fabric Structures Part V: Geometrical Modeling of Tuck Stitches", *Textile Research Journal*, Vol.78, No.7, 577-582, 2008.
- [11] Ajeli, S., Jeddi, Ali. A. A. and Rastgo, A. A., "Three-Dimensional Analysis of Loop Knit Structure by Using a Property of the Buckled-Twisted Elastic Rod. *Journal of the Textile Institute*, Vol.100, No.2, 111-119, 2009.
- [12] Durville, D., "Simulation of the Mechanical Behavior of Woven Fabrics at the Scale of Fibers", *International Journal of Material Forming*, Vol.3, Issue: S2, 1241-1251, 2010.
- [13] Durville, D., "Contact-friction Modeling within Elastic Beam Assemblies: an Application to Knot Tightening", *Computational Mechanics*, Online First, 2012.
- [14] Robitaille, F., Long, A.C., Jones, I.A. and Rudd, C.D., "Automatically Generated Geometric Descriptions of Textile and Composite Unit Cells", *Composites: Part A*, Vol.34, 303-312, 2003.
- [15] Lomov, S. V., Moesen, M., Stalmans, R., Trzcinski, G., Humbeeck, J.V. and Verpoest, I., "Finite Element Modeling of SMA Textiles: Super elastic Behavior", *The Journal of the Textile Institute*, Vol.102, No.3, 232-247, 2011.
- [16] Bishop, K. E. and Drucker, D. C., "Large deflection of cantilever beams", *Quarterly of Applied Mathematics*, Vol.3, No.3, 272-275, 1945.
- [17] Sivanandam, S.N. and Deepa, S.N., "Introduction to Genetic Algorithm", Springer, First Edition, 2008.
- [18] Zienkiewicz, O.C. and Tylor, R.L., "The finite element method-Volume 1: The Basis", Butterworth-Heinem.

AUTHORS' ADDRESSES

Ramin Bakhshpour

Saeed Ajeli, PhD

Hossein Hasani

Ali Asghar Asgharyan Jeedi

Department of Textile Engineering

Isfahan University of Technology

Daneshgah St.

Isfahan, Isfahan 84156-83111

IRAN